



Technical Data Sheet

ATI 718 HS™ & DA™ Alloys

INTRODUCTION

ATI 718-HS & 718-DA alloys (UNS N07718) are a family of thermo-mechanically processed materials that give higher mechanical properties to this already versatile alloy. To achieve these higher property levels, very tight controls must be observed over all processing parameters. Although double melt practices (VIM/VAR) are appropriate for many applications, improved cleanliness is achieved in the most critical applications by triple melting (VIM/ESR/VAR). Typical applications are highly stressed components in the compressor and turbine sections of jet engines.

SPECIFICATIONS

- GE C50TF81
- GE C50TF103
- GE C50TF104
- PWA 1085

PHYSICAL PROPERTIES

Melting Range:

2,300-2,450° F; (1,260 - 1,343° C)

Density:

0.296 lbs/in³ ; 8.19 gm/cm³

HEAT TREATMENT

- For high strength processed material (718-HS)
Solution treat at 1,725 - 1,875° F (941 - 1,024° C) for 1-2 hours. Rapid cool.
Age at 1,325° F (718° C) for 8 hours. Furnace cool to 1,150 F (621° C).
- For direct age processed material (718-DA)
Age at 1,325° F (718° C) for 8 hours. Furnace cool to 1,150° F (621° C). Hold 8 hours. Air cool. Rapid cool after final hot working operations.
No solution treating is required.

HARDNESS

The hardness in the solution treated condition is about 20-25 HRc which increases upon aging to about 40-47 HRc max.

FORGEABILITY/FORMABILITY

ATI 718-HS & DA alloys display good hotworking characteristics. Recommended forging furnace temperatures for initial forgings are 1,875° F (1,024° C) maximum for initial forging and 1,775-1,850° F (968 - 982° C) for finish forging. A reduction of 25% minimum during final forging, together with a low finishing temperature, is required to avoid a duplex grain structure and to establish proper mechanical properties. Time at temperature must be controlled to minimize delta phase precipitation.

This alloy is readily formable in the solution treated condition because of its good ductility.

Data are typical, are provided for informational purposes, and should not be construed as maximum or minimum values for specification or for final design, or for a particular use or application. The data may be revised anytime without notice. We make no representation or warranty as to its accuracy and assume no duty to update. Actual data on any particular product or material may vary from those shown herein. U.S. and foreign patents; other patents pending. TM is trademark of and ® is registered trademark of ATI Properties, Inc. or its affiliated companies. ® The starburst logo is a registered trademark of ATI Properties, Inc. © 2014 ATI. All rights reserved..



Technical Data Sheet

MACHINABILITY

ATI 718-HS & DA alloys are readily machinable in both the solution treated and age-hardened conditions.

WELDABILITY





Satisfactory welds can be produced in both the solution treated and fully-aged conditions using inert gas-shielded arc, plasma arc, electron beam, and resistance welding techniques. Because of the sluggish aging response, ATI 718-HS & DA alloys can be welded without hardening during the heating and cooling cycles, and the aged alloy can be repair welded several times without cracking even in complex weldments.

SPECIAL PRECAUTIONS

All lubricants, or coolants, particularly sulfur-bearing, should be removed prior to heat treating and welding.

Chemical Composition



	C	Mn	Si	S	P	Cr	Ni	Co	Fe	Mo	Ti	Al	B	Cb + Ta
% w/w, min.	-	-	-	-	-	17.00	50.0	-	Bal	2.8	0.65	0.20	-	5.0
% w/w, max.	0.08	0.35	0.035	0.015	0.015	21.00	55.0	1.0	-	3.3	1.15	0.80	0.006	5.5

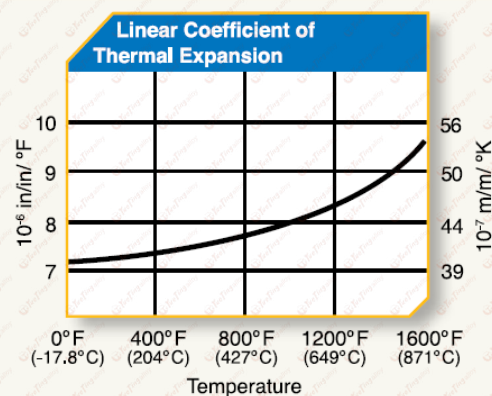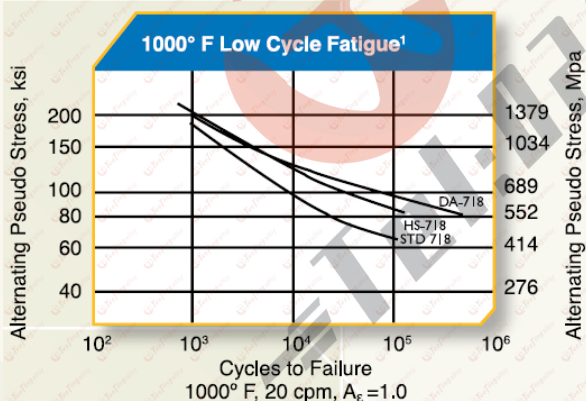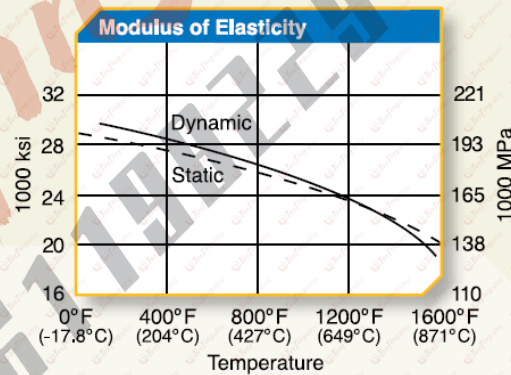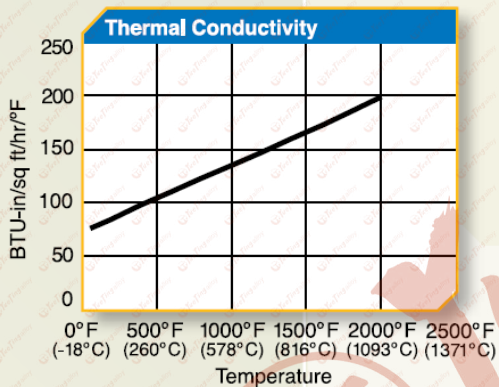

Data are typical, are provided for informational purposes, and should not be construed as maximum or minimum values for specification or for final design, or for a particular use or application. The data may be revised anytime without notice. We make no representation or warranty as to its accuracy and assume no duty to update. Actual data on any particular product or material may vary from those shown herein. U.S. and foreign patents; other patents pending. TM is trademark of and ® is registered trademark of ATI Properties, Inc. or its affiliated companies. © The starburst logo is a registered trademark of ATI Properties, Inc. © 2014 ATI. All rights reserved..



Technical Data Sheet

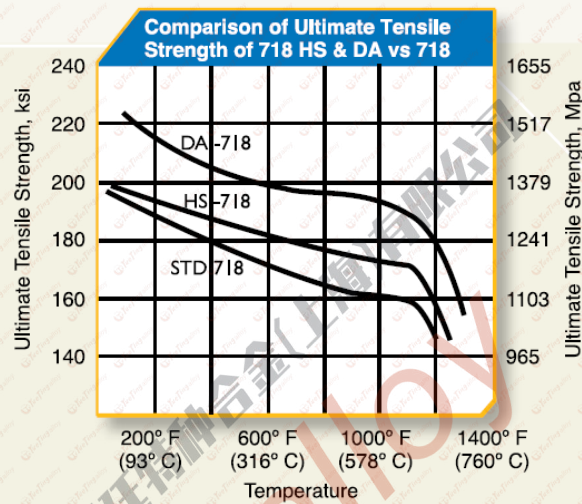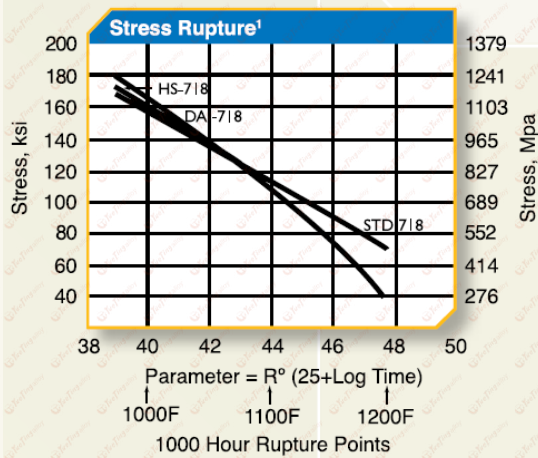

1. Krueger, D.D., "The Development of Direct Age 718 for Gas Turbine Engine Disk Applications", GE Aircraft Engines, Cincinnati OH, (TMS, 1989)

Data are typical, are provided for informational purposes, and should not be construed as maximum or minimum values for specification or for final design, or for a particular use or application. The data may be revised anytime without notice. We make no representation or warranty as to its accuracy and assume no duty to update. Actual data on any particular product or material may vary from those shown herein. U.S. and foreign patents; other patents pending. TM is trademark of and ® is registered trademark of ATI Properties, Inc. or its affiliated companies. ® The starburst logo is a registered trademark of ATI Properties, Inc. © 2014 ATI. All rights reserved..