

# SANDVIK 3R12 FORMED MEDICAL APPLICATIONS TUBE AND PIPE, SEAMLESS

## DATASHEET

Sandvik 3R12 is an austenitic stainless chromium-nickel steel with a low carbon content used for medical and dental instruments. The grade is characterized by:

- Good corrosion resistance
- Excellent toughness
- Good welding properties

### STANDARDS

- ASTM: TP304, TP304L
- UNS: S30400, S30403
- EN Number: 1.4301, 1.4306
- W.Nr.: 1.4301, 1.4306
- DIN: X5 CrNi 18 10, X2CrNi 19 11
- SS: 2333, 2352
- AFNOR: Z 2 CN 18.10
- BS: 304S11, 304S31
- JIS: SUS304L, SUS304LTB, SUS304TP

### Product standards

- ASTM F899, A213, A269, A312
- ISO 16061
- JIS G3459, G3463
- EN 10216-5
- BS 3605, 3606
- DIN 17456, 17458
- NFA 49-117, 49-217
- SS 14 23 52, 14 23 33

### Approval

JIS approval for Stainless Steel Tubes

### CHEMICAL COMPOSITION (NOMINAL) %

#### Chemical composition (nominal) %

C	Si	Mn	P	S	Cr	Ni
≤0.030	0.5	1.3	≤0.030	≤0.015	18.5	10

Subject to agreement, material with extra low Co content can be supplied.

## CORROSION RESISTANCE

### General corrosion

Sandvik Bioline 3R12 has good resistance in

- Organic acids at moderate temperatures
- Salt solutions, e.g. sulfates, sulphides and sulphites.
- Caustic solutions at moderate temperatures

Sandvik Bioline 3R12 has better resistance than normal type AISI 304 to oxidizing agents, such as nitric acid. Figure 1 shows iso-corrosion in nitric acid for Sandvik Bioline 3R12.

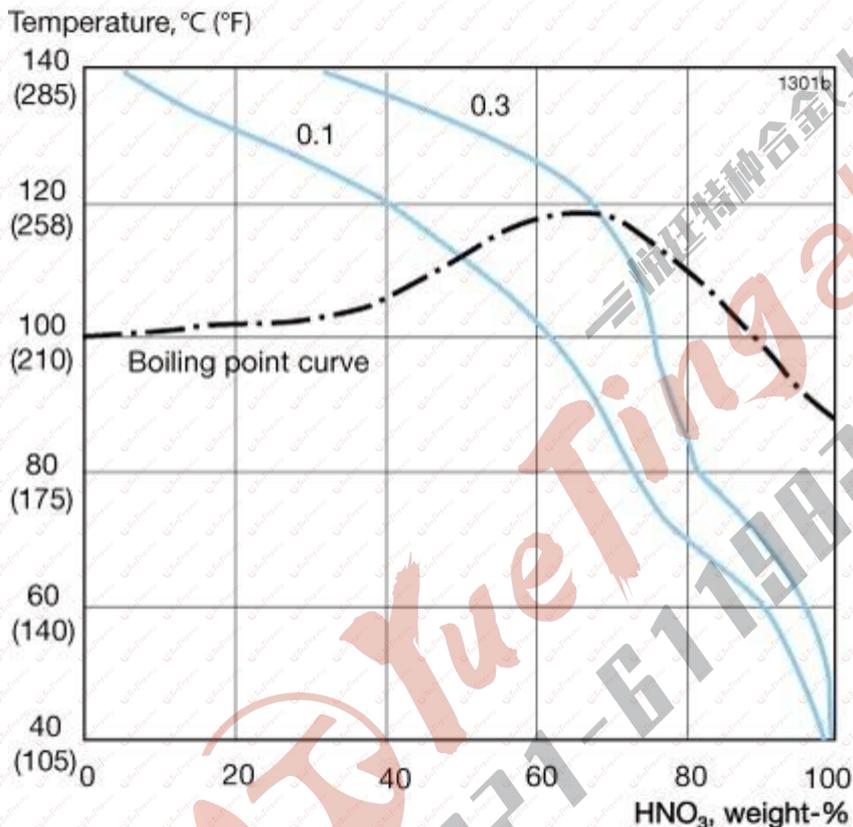


Figure 1. Diagram showing iso-corrosion in nitric acid for Sandvik Bioline 3R12 at the corrosion rates of 0.1 mm/year (4mpy) and 0.3 mm/year (12mpy).

### Intergranular corrosion

Sandvik Bioline 3R12 has a low carbon content and therefore better resistance to intergranular corrosion than steels of type AISI 304.

The TTC-diagram, Figure 2, which shows the result of testing for 24 hour in boiling Strauss solution (12% sulfuric acid, 6% copper sulphate) confirms the superior resistance of Sandvik Bioline 3R12. This is an advantage in complicated welding operations.

The good resistance against intergranular attack of Sandvik Bioline 3R12 is also demonstrated in the Huey test (boiling in 65% nitric acid for 5x48h).

A maximum corrosion rate of 0.40 mm/year in the annealed condition and 0.60 mm/year in the sensitized (675°C) condition can be met.

Sandvik Bioline 3R12 with its controlled and low impurity level, shows better results than ordinary AISI 304L or 321.

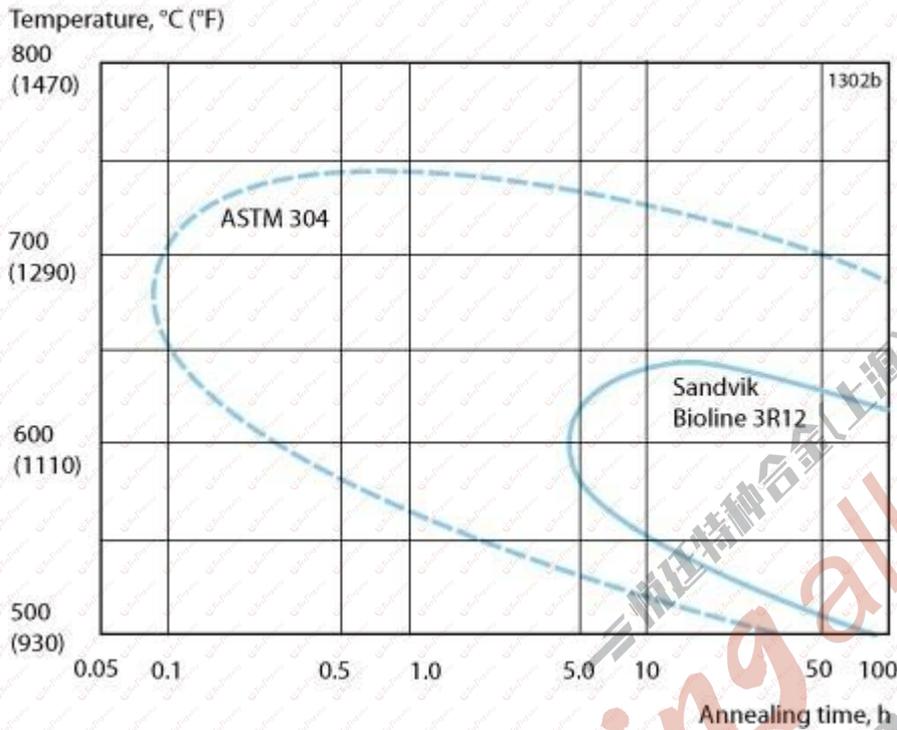


Figure 2. TTC-diagram for Sandvik Bioline 3R12 (AISI 304L) and AISI 304.

#### Pitting and crevice corrosion

The steel may be sensitive to pitting and crevice corrosion even in solutions of relatively low chloride content. Molybdenum-alloyed steels have better resistance improves with increasing molybdenum content.

#### Stress corrosion cracking

Austenitic steels are susceptible to stress corrosion cracking. This may occur at temperatures above about 60°C (140°F) if the steel is subjected to tensile stresses and at the same time comes into contact with certain solutions, particularly those containing chlorides. Such service conditions should therefore be avoided. Conditions when plants are shut down must also be considered, as the condensates which are then formed can develop conditions that leads to both stress corrosion cracking and pitting.

In applications demanding high resistance to stress corrosion cracking we recommend the austenitic-ferritic steel Sandvik SAF2304.

#### Gas corrosion

Sandvik Bioline 3R12 can be used in

- Air up to 850°C (1560°F)
- Steam up to 750°C (1380°F)
- Synthesis gas (ammonia synthesis) up to about 550°C (1020°F).

Creep behavior should also be taken into account when using the steel in the creep range.

In flue gases containing sulphur, the corrosion resistance is reduced. In such environments the steel can be used at temperatures up to 600-750°C (1110-1380°F) depending on service conditions. Factors to consider are whether the atmosphere is oxidizing or reducing, i.e. the oxygen content, and whether impurities such as sodium

and vanadium are present.

### APPLICATIONS

Thick wall tubes applications :

Sandvik 3R12 is used for medical and dental tools.

Thin wall tubes applications :

Sandvik 3R12 can be used for biopsy punches, mammography machine, brooches, suspension for oxygen tank for hospital mobile beds, surgical and dental tools.

### FORMS OF SUPPLY

Dimension range for tubes, thick wall

Seamless tube and pipe in Sandvik 3R12 is supplied in dimensions up to 260 mm outside diameter in the solution annealed and white-pickled condition or solution annealed in a bright-annealing process.

U-tubes can be delivered on request.

---

Sandvik 3R12 is stocked in a wide range of sizes according to ISO and ANSI.

Details of our manufacturing and stock programme are given in catalogue S-110-ENG.

---

Dimension range for tubes, thin wall

OD : 0.5 - 50.80 mm

thickness : 0.1 - 3 mm Fine tube tolerances :

- Thickness tolerance : +/- 10%
- OD tolerance : +/- 0.75% with a minimum of +/- 0.02 mm
- Roughness  
for OD > 5 mm Ra (outside) < 0.4 (by polishing)  
for ID > 3.2 mm Ra (inside) < 0.4 - this possibility depends on thickness/diameter ratio Specific roughness can be done on request
- Internal cleaning can not be done for inside diameter below 4 mm

All products supplied either in the annealed and cold worked condition to provide mechanical properties as required

### HEAT TREATMENT

The tubes are normally delivered in heat treated condition. If additional heat treatment is needed after further processing the following is recommended.

Stress relieving

850-950°C (1560-1740°F), cooling in air.

Solution annealing

1000-1100°C (1830-2010°F), rapid cooling in air or water.

### MECHANICAL PROPERTIES

Thin wall tubes

Sandvik 3R12 can be supplied in bright annealed or cold worked condition with a Rm : 860-1100 MPa

Thick wall tubes

For tube and pipe with wall thickness greater than 10 mm (0.4 in.) the proof strength may fall short of the stated value by about 10 MPa (1.4 ksi).



Imperial units

Temperature		Proof strength	
°F		Rp0.2	Rp1.0
		ksi	ksi
		min.	min.
200		24	28
400		20	24
600		18	22
800		16	20
1000		15	18

Creep strength

Temperature,		Creep-rupture strength (ISO- values)			
°C	°F	10 000 h		100 000 h	
		MPa	ksi	MPa	ksi
		approx.	approx.	approx.	approx.
550	1020	195	28.3	115	16.6
575	1065	147	21.3	93	13.5
600	1110	122	17.6	74	10.7
625	1155	100	14.5	58	8.4
650	1200	79	11.5	45	6.5
675	1245	64	9.2	33	4.8
700	1290	48	7.0	23	3.3

**PHYSICAL PROPERTIES**

Density: 7.9 g/cm<sup>3</sup>, 0.29 lb/in<sup>3</sup>

**Thermal conductivity**

Temperature			
°C	°F	W/m °C	Btu/ft h °F
20	68	15	8.5
100	200	16	9.5
200	400	18	10.5
300	600	20	12
400	800	22	13
500	1000	23	14
600	1200	25	15
700	1300	26	15

**Specific heat capacity**

Temperature			
°C	°F	J/kg °C	Btu/lb °F

### Specific heat capacity

Temperature			
°C	°F	J/kg °C	Btu/lb °F
20	68	475	0.11
100	200	500	0.12
200	400	530	0.13
300	600	560	0.13
400	800	580	0.14
500	1000	600	0.14
600	1200	615	0.15
700	1300	625	0.15

### Thermal expansion 1)

Temperature, °C	Per °C	Temperature, °F	Per °F
30-100	16.5	86-200	9
30-200	17	86-400	9.5
30-300	17.5	86-600	10
30-400	18	86-800	10
30-500	18.5	86-1000	10
30-600	18.5	86-1200	10.5
30-700	19	86-1400	10.5

1) Mean values in temperature ranges (x10<sup>-6</sup>)

### Modulus of elasticity

Temperature			
°C	°F	MPa	ksi
20	68	200	29.0
100	200	194	28.2
200	400	186	26.9
300	600	179	25.8
400	800	172	24.7
500	1000	165	23.5

### BENDING

Annealing after cold bending is not normally necessary, but this point must be decided with regard to the degree of bending and the operating conditions. Heat treatment, if any, should take the form of stress relieving or solution annealing, see under heat treatment.

Hot bending is carried out at 1100-850°C (2010-1560°F) and should be followed by solution annealing.

### WELDING

The weldability of Sandvik 3R12 for medical application is good. Welding must be carried out without preheating and subsequent heat treatment is normally not required. Suitable methods of fusion welding are gas-shielded arc welding TIG/GTAW and MIG/GMAW, with the TIG/GTAW method as first choice.

For Sandvik 3R12, heat input of <math><2.0 \text{ kJ/mm}</math> and interpass temperature of <math><150^\circ\text{C}</math> (300°F) are recommended.

Recommended filler metals  
TIG/GTAW or MIG/GMAW welding

ISO 14343 S 19 9 L / AWS A5.9 ER308L (e.g. Exaton 19.9.L)

---

Disclaimer: Sandvik is not providing any products or services that are intended or may be construed to be recommending or otherwise advising on, in any manner, the design, suitability, appropriateness or effectiveness, from a medical/biological/safety perspective, of any medical material, instrument and/or medical device.

YueTing alloy  
Tel: 021-61198229  
上海特种合金(上海)有限公司